**Industrial coating**

**Anti-corrosion coating, water-based, white
single-layer system, direct-to-metal (DTM)**


gloss retention and mechanical flexibility, without talc

Basis Alkyd resin

		Filler combination calcium carbonate with		
		HAR*- Talc (Comparison)	SILLITIN Z 89	TP 2008106
		[13]	[14]	[15]
Pigment preparation	L 00063.1			
	-- part 1 --			
	Demineralized water	8.60	8.60	8.60
	Edaplan 490 (1)	1.00	1.00	1.00
	Byk-349 (2)	0.20	0.20	0.20
	Byk-024 (2)	0.50	0.50	0.50
	AMP-90 (3)	0.20	0.20	0.20
	-- part 2 --			
	Omyacoat 850-OG (4)	2.00	2.00	2.00
	HAR-Talc)*	5.10	---	---
	SILLITIN Z 89 (5)	---	5.10	---
	TP 2008106 (5)	---	---	5.10
Let down	Kronos 2190 (6)	17.20	17.20	17.20
	-- part 3 --			
	Asconium 111 (7)	2.40	2.40	2.40
	-- part 4 --			
	WorléeSol E 330 W (8)	60.00	60.00	60.00
	Demineralized water	1.15	1.15	1.15
	Borchi OXY-Coat 1101 (9)	0.25	0.25	0.25
	Coapur 3025 (10)	1.60	1.60	1.60
	Ascotran-H10 (7)	0.20	0.20	0.20
	Total parts by weight	100.40	100.40	100.40

)* HAR = High Aspect Ratio

Recommendation [14] SILLITIN Z 89 for good price / performance ratio
[15] TP 2008106 (alkyl functionalized SILLITIN Z 89) with even better adhesion level comparable to talc



Preparation

- Pigment preparation
- mix raw materials from part 1
 - premix ingredients of part 2 and add to part 1. Disperse by dissolver with toothed disc under cooling for 15 min at high shear force
 - add raw material of part 3
- Let down
- for completion, add raw materials from part 4 in the order given to pigment preparation

Application

- dilution with 10 % demineralized water to reach viscosity level for compressed air spraying at 2 bar with 2 mm nozzle
- dry film thickness $\approx 60 \mu\text{m}$, single-layer coating on cold-rolled steel Q-Panel R 48

Conditioning


- Drying @ standard climate 23/50
- optical properties and adhesion: 7 days
 - pendulum hardness, corrosion tests: 14 days

Suppliers

- (1) Münzing Chemie
- (2) Byk Chemie
- (3) Advancion
- (4) Omya
- (5) HOFFMANN MINERAL
- (6) Kronos International
- (7) Ascotec
- (8) Worlée Chemie
- (9) Borchers
- (10) Coatex (Arkema)

More information on this topic:

[DTM: Neuburg Siliceous Earth in water-based corrosion protection - Alkyd single-layer coating, white](#)



Filler combination
calcium carbonate with

HAR*-
Talc
(Comparison)

SILLITIN
Z 89

TP
2008106

[13] [14] [15]

L00063.1

Technical Data

Solids content (w/w)
PVC

%
%

all: 51
all: 23

Properties

Dyn. viscosity 23 °C
0.1 s⁻¹ Pa·s
1000 s⁻¹ Pa·s

3.85 3.52 3.40
0.79 0.81 0.78

Pendulum hardness, Koenig
Cross-cut test 1 mm, tape tear-off

29 29 31
0 0-1 0-1

Color d/8° L*
a*
b*

95.5 96.0 95.9
-1.7 -1.7 -1.6
3.5 4.3 4.1

Gloss 60°
85°
after 48 h Humidity test, DIN EN ISO 6270-2 CH
60°
85°

GU GU
51 81 82
88 95 93
GU GU
23 67 71
47 91 91

Salt spray test, DIN EN ISO 9227 NSS, 160 h

Cross-cut test 1 mm, tape tear-off, after 24 h

0 1 0

Rating acc. DIN EN ISO 4628 Part 2-5:

Blistering, cracking, flaking


all: 0 (S0)

Rusting

all: Ri 0

Scribe: Sikkens 1 mm

delaminated

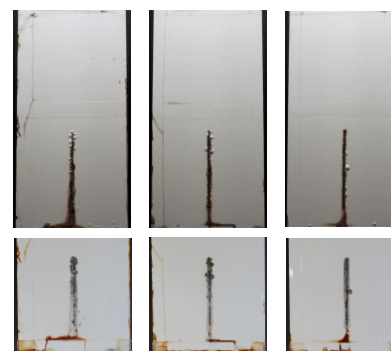

Delamination at scribe

all: < 3 mm

Corrosion at scribe

all: very low

Cupping, Erichsen
after 7 days standard climate 23/50

mm

50 66 67

Our applications engineering advice and the information contained in this formulation are based on experience and are made to the best of our knowledge and belief, they must be regarded however as non-binding advice without guarantee. Working and employment conditions over which we have no control exclude any damage claim arising from the use of our data and recommendations. Furthermore we cannot assume any responsibility for patent infringements, which might result from the use of our information.